arXiv:1208.3117v1 [cond-mat.soft] 15 Aug 2012

Stretchable liquid crystal blue phases

F. Castles, S. M. Morris, J. M. C. Hung, M. M. Qasim, and H. J. Coles
Centre of Molecular Materials for Photonics and Electronics,
Department of Engineering, University of Cambridge,
9 JJ Thomson Avenue, Cambridge CB3 0FA, United Kingdom

We report the fabrication of a stretchable blue phase in a cross-linked liquid crystalline system. A 20-micron-thick film was reversibly stretched by up to 1.5 times its initial length. A concomitant blue-shift of the selectively-reflected color was observed.

Stretchable materials made from cross-linked liquid crystalline systems have been demonstrated in the nematic, chiral nematic, and smectic mesophases [1, 2]. The purpose of this Letter is to report preliminary results on the fabrication of a stretchable cross-linked liquid crystalline blue phase.

The details of the fabrication process are described in the Methods section below. The polymer was formed and cross-linked via photopolymerization of a mixture which included mono- and di-functional reactive mesogens (mono- and di-acrylates). Following work by Broer *et al.* [3], photopolymerization of reactive mesogens has been used to stabilize a wide variety of liquid crystals—including the blue phases—and to increase their functionality [4–7]. The technique has been reported as an established method to create monodomain chiral nematic elastomers [8]. Using this method, we were able to form a high-quality (large monodomain) blue phase by slow-cooling before subsequent polymerization and cross-linking.

The materials and polymerization process are very similar to those we have used recently to form blue phase templates [9]. In particular, we used bimesogens, exploiting their unusually stable intrinsic blue phases [10, 11] which were sufficiently robust under the required high-intensity ultraviolet exposure. After photopolymerization the material appeared macroscopically as a solid, stable over a wide temperature range including room temperature. The structure was identified conclusively as that of blue phase I using a combination of standard techniques: polarizing optical microscopy, spectral analysis, and Kossel diffraction analysis.

Figure 1 shows a film of the blue phase polymer being stretched. Here, a 20 μm-thick layer was placed across a variable-width aperture and observed on a polarizing optical microscope. A characteristic blue phase platelet texture [12] is apparent. The film adhered to the aperture edges and was stretched as the aperture was widened. So far we have succeeded in stretching the films in this way by up to 1.5 times their original length. The stretching was carried out at room temperature and was reversible; the photograph in Fig. 1(a) was taken after a number of stretch-relax cycles.

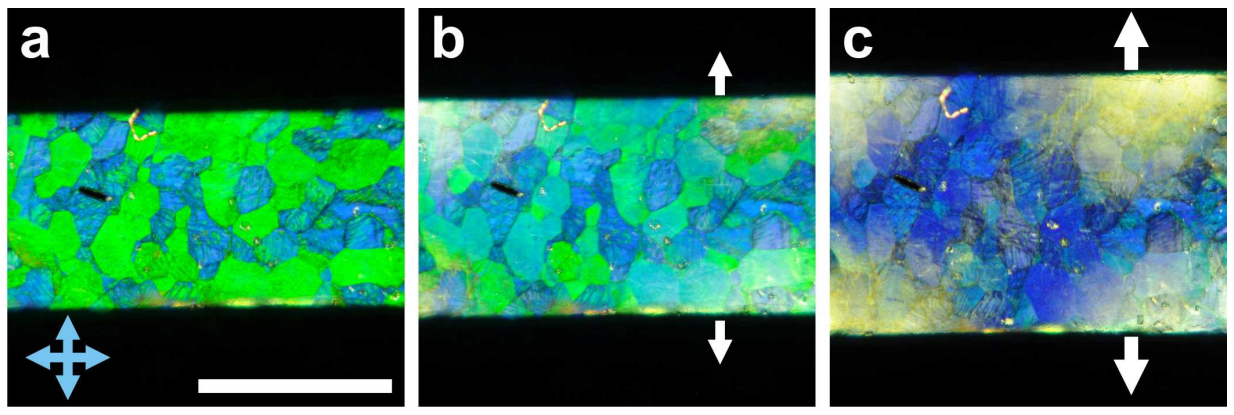

FIG. 1. Stretchable blue phase between crossed polarizers. A 20 μm thick layer of the blue phase material was placed across a variable-width aperture and imaged in transmission using an optical polarizing microscope (scale bar, 1 mm). (a) The un-stretched state. Pale blue arrows denote the orientation of the crossed polarizers. (b) & (c) The aperture was widened in the direction of the white arrows, stretching the sample. A blue-shift of the color is observed, together with enhanced transmission in some areas of the film due to inhomogeneous strain-induced birefringence.

Two interesting features are qualitatively demonstrated in the Figure: a blue-shift of the color and inhomogeneous strain-induced birefringence. Quantitative analysis of these features, and further details, will be published in the future.

Methods

The material was composed of 4 % chiral additive BDH1281 (Merck), 30 % reactive-mesogen/photoinitiator mixture UCL-011-K1 (DIC Corp.), 16.5 % FFO5OFF, 16.5 % FFO7OFF, 16.5 % FFO9OFF, and 16.5 % FFO11OFF (where the chemical structure of the bimesogens FFO*n*OFF, synthesized in-house, is shown in the Supplementary Information of Ref. [9]). The mixture was filled between two sheets of glass, forming a film 20 μm thick. The blue phase was formed by slow cooling from the isotropic phase. The material was polymerized under ultraviolet radiation (Omnicure series 1000 spot curing system with 320–500nm filter, EXFO) using light of intensity 50 W/m^2 (measured using a PM 100 digital optical powermeter, Thorlabs). A two step process was employed: First, the blue phase was exposed for 7 s at an elevated temperature. Second, it was exposed for 13 s at room temperature. After removal of one glass layer, the film was separated from the other glass layer using a razor blade wetted with propan-2-ol.

Acknowledgments

This work was carried out under the COSMOS project which is funded by the Engineering and Physical Sciences Research Council UK (Grants No. EP/D04894X/1 and No. EP/H046658/1). We thank H. Hasebe (DIC Corp., Japan) for supplying the reactive mesogen UCL-011-K1. S.M.M. acknowledges The Royal Society for financial support.

[1] H. Finkelmann, H.-J. Kock, and G. Rehage, Makromol. Chem. Rapid Commun. **2**, 317 (1981).
[2] M. Warner and E. M. Terentjev, *Liquid Crystal Elastomers* (Oxford University Press, Oxford, 2007).
[3] D. J. Broer, H. Finkelmann, and K. Kondo, Makromol. Chem. **189**, 185 (1988).
[4] H.-S. Kitzerow, H. Schmid, A. Ranft, G. Heppke, R. A. M. Hikmet, and J. Lub, Liq. Cryst. **14**, 911 (1993).
[5] D. J. Broer, J. Lub, and G. N. Mol, Nature (London) **378**, 467 (1995).
[6] R. A. M. Hikmet and H. Kemperman, Nature (London) **392**, 476 (1988).
[7] H. Kikuchi, M. Yokota, Y. Hisakado, H. Yang, and T. Kajiyama, Nature Mater. **1**, 64 (2002).
[8] E. M. Terentjev, in *Cross-Linked Liquid Crystalline Systems*, edited by D. J. Broer, G. P. Crawford, and S. Zumer (CLC Press, Boca Raton, 2011) p. 369.
[9] F. Castles, F. V. Day, S. M. Morris, D.-H. Ko, D. J. Gardiner, M. M. Qasim, S. Nosheen, P. J. W. Hands, S. S. Choi, R. H. Friend, and H. J. Coles, Nature Mater. **11**, 599 (2012).
[10] H. J. Coles and M. N. Pivnenko, Nature (London) **436**, 997 (2005).
[11] F. Castles, S. M. Morris, E. M. Terentjev, and H. J. Coles, Phys. Rev. Lett. **104**, 157801 (2010).
[12] I. Dierking, *Textures of Liquid Crystals* (Wiley-VCH, Weinheim, 2003) p. 45.